


# LOW-P™ CEMENT

Low Permeability Cement

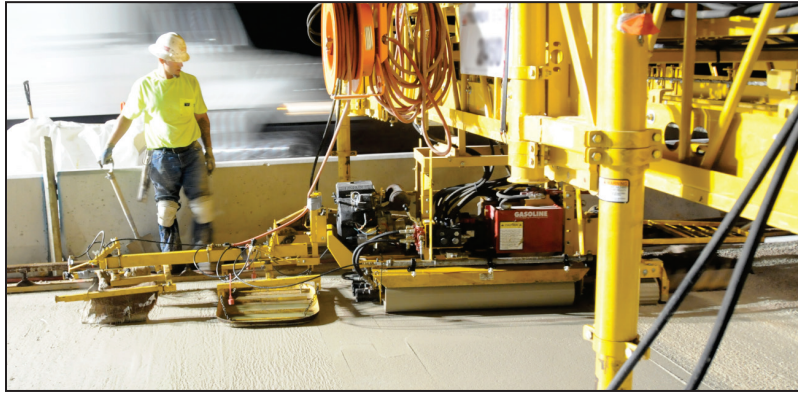

## PRODUCT DATASHEET

**DESCRIPTION:** Rapid Set® LOW-P™ Cement is a low permeability, corrosion inhibiting, fast-setting hydraulic cement. When mixed with water and aggregates, Low-P Cement produces concrete mixtures with unparalleled performance and ease of use. The finished Low-P Cement concrete exhibits exceptional long-life durability in harsh freeze-thaw conditions.

**APPLICATIONS:** Low-P Cement is ideal for fast-track bridge deck overlays, pavement repairs, elevated deck repairs, parking structures, marine structures, and other projects where low chloride ion permeability, corrosion resistance, and fast strength gain are desired. Low-P Cement is superior to portland cement latex modified concrete, low slump concrete, microsilica/silica fume concrete, and polyester concrete.

**ENVIRONMENTAL ADVANTAGES:** Use LOW-P Cement to reduce your carbon footprint and lower your environmental impact. Production of Rapid Set cement emits far less CO<sub>2</sub> than portland cement. Contact your CTS representative for EPD, LEED values and other sustainability information.

**SURFACE PREPARATION:** For repairs, application surface must be clean, sound and free from any materials that may inhibit bond, such as oil, asphalt, curing compound, acid, dirt and loose debris. Roughen surface and remove all unsound material. Apply Low-P Cement concrete to a thoroughly saturated surface. Standing water and puddles should be removed from the surface. Scrub coats or brush-in coats are not required.

**MIXING:** Low-P Cement concrete mixes may be batched using continuous volumetric mixer equipment or a weight batch mixer. Organize work so that all personnel and equipment are in place before mixing. Use clean potable water. Working time is approximately 15 to 20 minutes. CAUTION: Do not use additional fly ash or microsilica additives, or pozzolonic materials.

**PLACEMENT:** LOW-P Cement may be placed using traditional methods. Organize work so that all personnel and equipment are ready before placement. Place, consolidate, and screed quickly to allow for maximum finishing time. Do not wait for bleed water. Apply final finish as soon as possible. Low-P Cement concrete may be troweled, floated or broom finished. Use a method of consolidation that eliminates air voids. Roller and truss screeds can be used for small overlay placements. Self-propelled screed/finishing equipment should be used for all large applications. Patching and small overlay work may require additional internal vibration. Straight edge or bull floats can be used directly behind screed/finisher equipment to ensure closure of concrete surface. Surface retardants or water misting should be used to reduce evaporation. Broom or tine the concrete as soon as the surface can hold the finish applied. Do not install on frozen surfaces.

**COLD WEATHER:** Environmental and material temperatures below 70°F (21°C) may delay setting time and reduce the rate of strength gain. Lower temperatures will have a more pronounced effect. Thinner sections will be more significantly affected. To compensate for cold temperatures, keep material warm, use heated mix water and follow ACI 306 Procedures for Cold Weather Concreting.

**WARM WEATHER:** Environmental and material temperatures above 70°F (21°C) may speed setting time and increase the rate of strength gain. Higher temperatures will have a more pronounced effect. To compensate for warm temperatures, keep material cool, use chilled mix water and follow ACI 305 Procedures for Hot Weather Concreting. The use of retarding admixtures will help offset the effects of high temperatures.

## OVERVIEW

### Highlights:

Low Permeability: Less than 1000 coulombs

Fast: Minimizes downtime. Ready for traffic in 1 to 3 hours

Durable: Low shrinkage, non-metallic, no added chlorides, sulfate resistant, freeze-thaw resistant

Easy to place: High slump, non-segregating formula

Environmentally friendly: Lower carbon emissions

Corrosion Protection: Resistance to corrosion caused by chlorides (deicing salts)

Just add water and aggregate

### Approved:

State (DOT) and local approvals

### MasterFormat®

03 01 30 Maintenance of Cast-in-Place Concrete

03 01 50 Maintenance of Cast Decks and Underlayment

03 01 70 Maintenance of Mass Concrete

03 31 00 Structural Concrete Cast-in-Place

03 53 19 Concrete Overlayment

### Manufacturer:

CTS Cement Manufacturing Corp.  
12442 Knott St.  
Garden Grove, CA 92841  
Tel: 800-929-3030 | Fax: 714-379-8270  
Web: www.CTScement.com  
E-mail: info@CTScement.com



# LOW-P™ CEMENT

Low Permeability Cement

**CURING:** Most materials made with LOW-P CEMENT must be cured. Best practices include water curing or the use of curing compounds that comply with ASTM C309 Type 2 Class B such as poly-alphamethylstyrene (PAMS). Begin curing after the material starts to harden and before the surface starts to lose its moist sheen. The objective of water curing is to maintain the moist sheen on the entire surface until the product has achieved sufficient strength. Keep exposed surfaces wet for a minimum of 1 hour. When experiencing extended setting time due to cold temperature or the use of retarder, longer curing times may be required. The user is responsible for the mix design and determining the appropriate curing method.

**FIELD TESTS:** It is recommended to conduct field test panels at the jobsite using the prepared substrate and the approved LOW-P Cement concrete mix design to determine actual field performance and suitability for the intended use.

**AVAILABILITY:** Low-P Cement is available nationwide in 2000-lb bulk bags and 50-lb bags.

**STORAGE & SHELF LIFE:** LOW-P Cement has a shelf life of 12 months when stored properly in a dry location, protected from moisture, out of direct sunlight, and in an undamaged package.

**USER RESPONSIBILITY:** Before using CTS products, read current technical data sheets, bulletins, product labels and safety data sheets at [www.CTScement.com](http://www.CTScement.com). It is the user's responsibility to review instructions and warnings for any CTS products prior to use.

**WARNING: DO NOT BREATHE DUST. AVOID CONTACT WITH SKIN AND EYES.** Use material in well-ventilated areas only. Exposure to cement dust may irritate eyes, nose, throat, and the upper respiratory system/lungs. Silica exposure by inhalation may result in the development of lung injuries and pulmonary diseases, including silicosis and lung cancer. Seek medical treatment if you experience difficulty breathing while using this product. The use of a NIOSH/MSHA-approved respirator (P-, N- or R-95) is recommended to minimize inhalation of cement dust. Eat and drink only in dust-free areas to avoid ingesting cement dust. Skin contact with dry material or wet mixtures may result in bodily injury ranging from moderate irritation and thickening/cracking of skin to severe skin damage from chemical burns. If irritation or burning occurs, seek medical treatment. Protect eyes with goggles or safety glasses with side shields. Cover skin with protective clothing. Use chemical resistant gloves and waterproof boots. In case of skin contact with cement dust, immediately wash off dust with soap and water to avoid skin damage. In case of skin contact with wet cement, wash exposed skin areas with cold running water as soon as possible. In case of eye contact with cement dust, flush immediately and repeatedly with clean water, and consult a physician. If wet cement splashes into eyes, rinse eyes with clean water for at least 15 minutes and go to the hospital for further treatment.

Please refer to the SDS and [www.CTScement.com](http://www.CTScement.com) for additional safety information regarding this material.

**LIMITED WARRANTY:** CTS CEMENT MANUFACTURING CORP. (CTS) warrants its materials to be of good quality and, at its option, will replace or refund the purchase price of any material proven to be defective within one (1) year from date of purchase. The above remedies shall be the limit of CTS' responsibility. Except for the foregoing, all warranties expressed or implied, including merchantability and fitness for a particular purpose, are excluded. CTS shall not be liable for any consequential, incidental, or special damages arising directly or indirectly from the use of the materials.

**⚠ WARNING:** Can expose you to crystalline silica, a carcinogen, and hexavalent chromium, a reproductive toxicant. See [www.P65Warning.ca.gov](http://www.P65Warning.ca.gov).

## TYPICAL PHYSICAL DATA

### MIX DESIGNS

Low-P™ Cement	658 lbs (298 kg)
Coarse Aggregate 3/8" - 1/2"	1450 lbs (658 kg)
Fine Aggregate	1600 lbs (726 kg)
Cement Retarder*	2.4 lb (1.08 kg)
Water	296 lbs (134 kg)

### PHYSICAL DATA

#### Set Time, ASTM C191 Mod.

Initial set	30 minutes
Final set	40 minutes

#### Slump, ASTM C143

7-9 inches

#### Compressive Strength, ASTM C39

3 hours	4500 psi (31.0 MPa)
6 hours	6000 psi (41.4 MPa)
24 hours	7000 psi (48.3 MPa)
7 days	8000 psi (55.2 MPa)
28 days	9000 psi (62.1 MPa)

#### Bond Strength, ASTM C882 per C928

24 hours	1200 psi (8.27 MPa)
7 days	1900 psi (13.1 MPa)
28 days	2200 psi (15.21 MPa)

#### Shrinkage, ASTM C157

7 days	0.003%
28 days	0.023%

#### Freeze-Thaw, ASTM C666 (Procedure A)

300 cycles (Durability factor)	> 96%
-----------------------------------	-------

#### Rapid Chloride Ion Penetration, ASTM C1202

28 days	< 1000 Coulombs
---------	-----------------

\*Citric acid can be used to extend the setting time of Low-P™ Concrete. Please contact CTS Cement for dosage recommendations. Note: Performance will vary based on actual aggregate properties and project variables. Complete trial batches to verify performance. All data produced at 70°F (21°C).



USGBC and related logo is a trademark owned by the U.S. Green Building Council and is used by permission.